

UNCLASSIFIED

---

AD 297028

*Reproduced  
by the*

ARMED SERVICES TECHNICAL INFORMATION AGENCY  
ARLINGTON HALL STATION  
ARLINGTON 12, VIRGINIA



---

UNCLASSIFIED

NOTICE: When government or other drawings, specifications or other data are used for any purpose other than in connection with a definitely related government procurement operation, the U. S. Government thereby incurs no responsibility, nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use or sell any patented invention that may in any way be related thereto.

N-62-2-5

297028

297028

COPY NO. 78



PICATINNY ARSENAL TECHNICAL REPORT 3030

FEASIBILITY STUDY ON  
THE USE OF PLASTIC COMPONENTS FOR  
THE 81MM MORTAR BIPOD ASSEMBLY

MERRILL EIG

FEBRUARY 1963

ONS 9010.11.642

DA PROJECT 593-32-007

PICATINNY ARSENAL  
DOVER, NEW JERSEY

RECEIVED  
JAN 21 1963  
TSA

The findings in this report are not to be construed as  
an official Department of the Army position.

#### **DISPOSITION**

**Destroy this report when it is no longer needed.  
Do not return.**

#### **ASTIA AVAILABILITY NOTICE**

**Qualified requesters may obtain copies of this report  
from ASTIA.**

FEASIBILITY STUDY ON  
THE USE OF PLASTIC COMPONENTS  
FOR THE 81 MM MORTAR BIPOD ASSEMBLY

Montell Eng

February 1963

Feltman Research Laboratories  
Picatinny Arsenal  
Dover, N. J.

Picatinny Arsenal Technical Report 3030

OMS 5610.11.842

Dept of the Army Project 592-32-007

Approved:

*J. D. Matlack*

J. D. MATLACK  
Chief, Plastic and  
Packaging Laboratory

# TABLE OF CONTENTS

	Page
Object	1
Summary	1
Conclusions	1
Recommendations	2
Introduction	2
Discussion	2
Appendices	
A	15
B	24
Distribution List	32
Tables	
1      Composition of component parts	12
2      Material design strength values	13
3      Strain data submitted by Watervliet Arsenal	14
Figures	
1      Bipod assembly (a) and yoke assembly (b)	8
2      Schematic of elevating mechanism	9
3      Connector	11
4      81 mm mortar	15
5      Schematic of force system	16
6      Moment diagram and edge view of bipod assembly	17
7      Force diagram	18
8      Bipod assembly	19
9      Assumed geometry of bipod assembly during firing	22

Wagon  
Covers

10	Cover	25
11	Tube	26
12	Housing tube connector	27
13	Bracket	28
14	Body	29
15	Case	30
16	Yoke ring	31

## OBJECT

To analyze strain gage data on the bipod assembly for the 81 mm mortar and to determine the feasibility of replacing heavy metal parts with lighter weight plastics.

## SUMMARY

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

The calculated maximum stresses were as follows: a bending stress of 20,100 psi on the case, and a 2,750 psi stress due to bending and a compressive stress of 22,000 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,000 psi and a shear stress of 13,000 psi.

Roller reinforced plastic tubing was suggested for fabrication of protractor type components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other as required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

## CONCLUSIONS

It may be concluded from this analysis that it is feasible to fabricate the desired components of the 81 mm mortar bipod assembly from plastic materials.



## RECOMMENDATIONS

It is recommended that prototype components be fabricated and tested under actual firing conditions to determine suitability of design. It is recommended that, upon acceptance of design, molds be fabricated and a glass filled epoxy-molding material such as Scotchply 1100 be used for production of end items requiring high strength.

## INTRODUCTION

The Plastics and Packaging Laboratory at Picatinny was requested by Watervliet Arsenal to analyze strain gage data obtained by Watervliet Arsenal on the bipod assembly for the 81 mm mortar and from such data, to determine the feasibility of replacing existing metal components of the mortar assembly with lightweight plastic parts. The use of high strength, lightweight plastics for this application was considered desirable as a means of lightening and making more portable an assembly designed for use and handling by infantry soldiers.

## DISCUSSION

The strain gage data received from Watervliet Arsenal was obtained during actual firings of the mortar. Rectangular strain rosettes consisting of three gages laid out at  $45^\circ$  and  $90^\circ$  angles to each other were used to measure strain on the bipod legs.

Two C-7 type strain gages in series  $180^\circ$  apart were used to measure strain on the deck of the base plate.

It was apparent, from data on the first 10 rounds, that the forces acting on the bipod legs are almost solely axial, i.e., tend to extend or compress the legs. In such a situation, the rosette gage is not needed. Therefore, on the remaining 10 rounds, only the strain recorded by the axial gage was used. Maximum positive and negative deflections were used and the stress values were computed as the product of strain and Young's Modulus (see Table 3, p 12).

Review of this reported strain gage data by Picatinny Arsenal indicated that the number of gages placed around the bipod legs was not sufficient for determining the actual maximum stress. Therefore, an engineering approach utilizing an iteration process was tried and successfully used (see Appendix A) to determine the maximum stress.

#### Determination of Tensile Bending ( $\sigma_{TB}$ ) and Compressive Stresses ( $\sigma_C$ ) in Right Leg

From the firing data reported to Picatinny Arsenal by Watervliet Arsenal, it was observed that the right leg of the bipod experienced a compressive load of 6670 psi after 11.4 milliseconds after firing (see Table 3). After 40.4 milliseconds, a stress reversal occurred in which this compressive stress changed to a tensile stress of 17,980 psi. It is important to note that the stresses reported in the data and substantiated by Watervliet Arsenal are the sums or resultants of the tensile bending stress ( $\sigma_{TB}$ ) and the compressive stress ( $\sigma_C$ ). It must therefore be assumed that there exists a tensile stress (due to bending) such that, when a compressive stress of 6,670 psi is added to it, the resultant is a tensile stress of 17,980 psi. The reason is that both tensile and compressive stresses can conceivably be applied simultaneously. Thus, by numerically adding the compressive and tensile stresses reported in the data, values for  $\sigma_{TB}$  and  $\sigma_C$  are determined (see Appendix A). For this particular example,  $\sigma_{TB}$  is determined to be 24,650 psi and  $\sigma_C$  is 6,770 psi. This procedure is continued for each of the six test rounds to determine  $\sigma_{TB}$  and  $\sigma_C$  for each case. Use of the maximum values of  $\sigma_{TB}$  and  $\sigma_C$  will represent the maximum possible loading condition which can be sensed by the right bipod leg. The values thus determined are:

$$\sigma_{TB} = 24,650 \text{ psi}$$

$$\sigma_C = 12,780 \text{ psi}$$

It is important to emphasize that these stress values are resultant stresses; each being the sum of a tensile bending stress and a compressive stress. Also, that it is possible to obtain these values from an infinite number of tensile and compressive stresses. For example, suppose the leg assembly is subjected simultaneously to a tensile bending stress of 17,980 psi and a compressive stress of 20,000 psi. The resultant stress would be 17,980 psi. It is seen that this is exactly the value of stress reported by the strain gage data, yet it is by no means the maximum stress.

as demonstrated, since the maximum recorded stress is a function of the time lag in applied loads. Similarly, a reverse procedure can be made to yield a negative value of stress, i.e., 6,770 psi.

In order to limit the many possible choices of bending and compressive stresses, it will be assumed, and reasonably so, that approximately 15% of the reactive force (or 12,000 lb) is transmitted to the bipod in the form of friction ( $F_f$ , see Fig 5). Having established this criterion, an iteration process will now be used to converge upon the final design stress values. This is accomplished by substituting various combinations of stresses the sum of which is a plus 17,980 psi into Equation 6 (Appendix A) until the desired value of  $F_f$  is obtained. When this condition is satisfied, the maximum design value for  $\sigma_{TB}$  is obtained. This same procedure is repeated for various values of stresses yielding a resultant stress of a minus 6,770 psi. Similarly, when these values are substituted into Equation 6 until the desired value of  $F_f$  is obtained, a maximum value of  $\sigma_C$  is also obtained.

It can be shown by this iteration process that there are two sets of values that will yield  $F_f$  equal to 12,000 pounds

$$(a) \quad \sigma_{TB} = 33,000 \text{ psi}$$

$$\sigma_C = 16,000 \text{ psi}$$

$$(b) \quad \sigma_{TB} = 3,000 \text{ psi}$$

$$\sigma_C = 15,760 \text{ psi}$$

Since the values in (a) represent the more extreme case, these values will be used for design purposes. It is interesting to note that they are in reasonably good agreement with the maximum values determined from the data; i.e.,  $\sigma_{TB} = 24,650 \text{ psi}$  and  $\sigma_C = 12,760 \text{ psi}$ .

From Equation 6, it is obvious that  $\sigma_C$  is the major contributing factor since the coefficient of  $\sigma_{TB}$  is very small compared to that of  $\sigma_C$ . For all practical purposes,  $F_f$  is a function of  $\sigma_C$  only. This fact also agrees with the comments reported on the data, to the effect that strain rosettes are not needed since most of the stress is compressive.

#### Determination of $\sigma_{TB}$ and $\sigma_C$ in Left Leg

The process for determining  $\sigma_{TB}$  and  $\sigma_C$  for the left leg is identical to that described for the right leg. The only difference is in the physical dimensions. The applicable parameters are listed below.

Moment of inertia (I)	.0328 in. <sup>4</sup>
Length of leg (l)	27 in.
Distance from neutral axis of leg to extreme fiber (c)	.476 in.
Area (A)	.404 in. <sup>2</sup>

Substitution of these values into Equation 5 (see Appendix A) yields the following equation for frictional force:

$$F_f = \sqrt{(26.2 \times 10^{-4}) \sigma_{TB}^2 + (.652) \sigma_C^2} \quad (1)$$

Using the iteration method, the maximum design stresses are determined to be

$$\sigma_{TB} = 44,000 \text{ psi}$$

$$\sigma_C = 17,000 \text{ psi}$$

Here again the stresses are in reasonably good agreement with those determined from the data

$$\sigma_{TB} = 27,260 \text{ psi}$$

$$\sigma_C = 11,890 \text{ psi}$$

Substituting the calculated values for  $\sigma_{TB}$  and  $\sigma_C$  into Equation 5 (in Appendix A) yields a frictional force for the right and left leg respectively,

$$F_{fR} = 12,540 \text{ lb}$$

$$F_{fL} = 13,560 \text{ lb}$$

$F_{avg} = 13,050$  pounds. Note that this value does not depart significantly from the 15% (or 12,000 pounds) originally assumed. If the calculated value for  $\sigma_C$  for left and right leg is substituted into Equation 2d and 4b respectively (Appendix A) an  $F'_{avg}$  of 15,140 pounds is obtained.

At this point, all the forces acting on the system are known and a detailed stress analysis can be made of the various components.

### Stresses Induced in Plastic Components

#### Hub Connection

It is contemplated that the yoke and the tube housing will be fastened to each other by bonding with an epoxy adhesive rather than by the use of screws. The applied load  $F'_{avg}$  will thus induce an interfacial shear stress (see Fig 1, pg 8).

$$\sigma_{sh} = \frac{F'_{avg}}{A} = \frac{15,140}{\pi Dh} = \frac{15,140}{\pi (1.6875) (1.75)} = 1,635 \text{ psi}$$

Which is well below the design value of 3000 psi for epoxy resins.

#### Case

Upon firing, shaft A (Fig 2, p 9) imparts a bearing load to the case, with a resulting bearing stress of

$$\sigma_{BR} = \frac{F'_{avg}}{A} = \frac{15,140}{\frac{\pi}{4} (1.6895^2 - 1.375^2)} = 20,100 \text{ psi}$$

#### Tube Housing

The force acting on the left leg, for a calculated stress of 44,000 psi is

$$R'_{fL} = (F_{TB})_L = \frac{\sigma_B 2I}{cl} = \frac{44,000 (2) (.0328)}{(.476) (27)} = 224 \text{ lb}$$

Similarly, a stress of 33,000 psi will induce a force in the right leg of

$$R'_{fR} = (F_{TB})_R = \frac{33,000(2)(.0498)}{(.563)(27)} = 216 \text{ lb.}$$

the average force being

$$(F_{TB})_{avg} = \frac{(F_{TB})_L + (F_{TB})_R}{2} = 220 \text{ lb.}$$

The tube housing shaft B (Fig 1) will act as a solid shaft during firing since shafts A and B are coaxial. The moment of inertia is

$$I_H = \frac{\pi}{64} (D)^4 = \frac{\pi}{64} (1.6895)^4 = .402 \text{ in.}^4$$

The stress due to bending in the tube housing is

$$\sigma_B = \frac{Mc}{I} = (F_{TB})_{avg} \frac{1c}{I} = \frac{(220) 6}{.402} \left( \frac{1.6895}{2} \right)$$

$$\sigma_B = 2,780 \text{ psi}$$

The bearing stress of 20,100 psi imparted to the case is the same compressive stress as exists in the housing. Thus the total stress in the tube housing is the sum of the bending and compressive stresses,

$$\sigma_T = \sigma_B + \sigma_C = 2,780 + 20,100 = 22,880 \text{ psi.}$$

It is to be noted that the cover and body and the yoke ring components do not sense any significant stresses since the only applied load is the inertia of their own weight. However, the yoke ring must withstand a sustained shear load at temperatures of 400°-500°F for periods of 15-30 minutes.

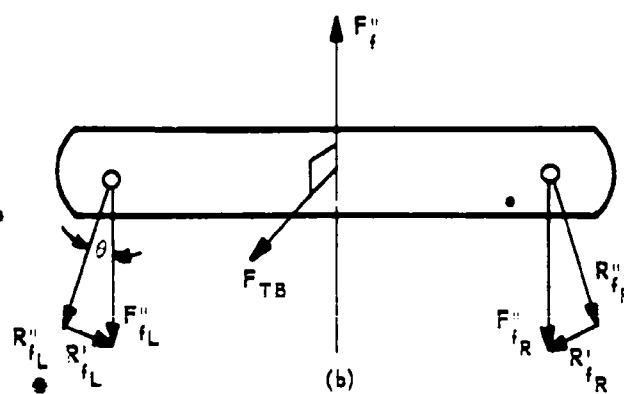
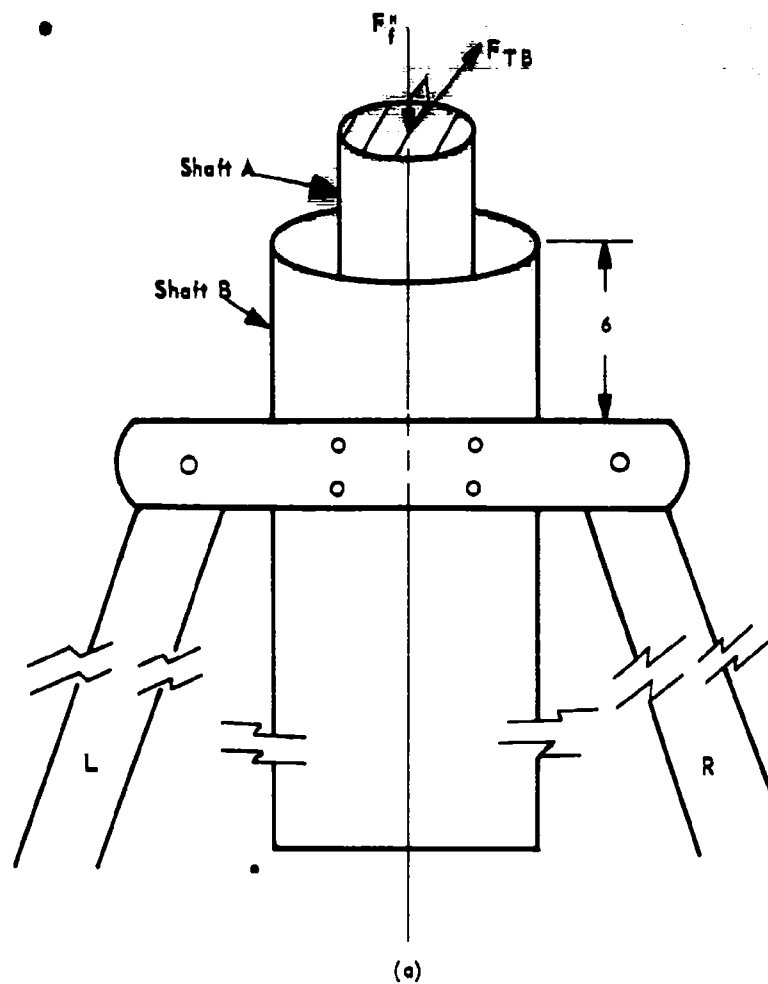


Fig 1 Bipod assembly (a) and yoke assembly (b)

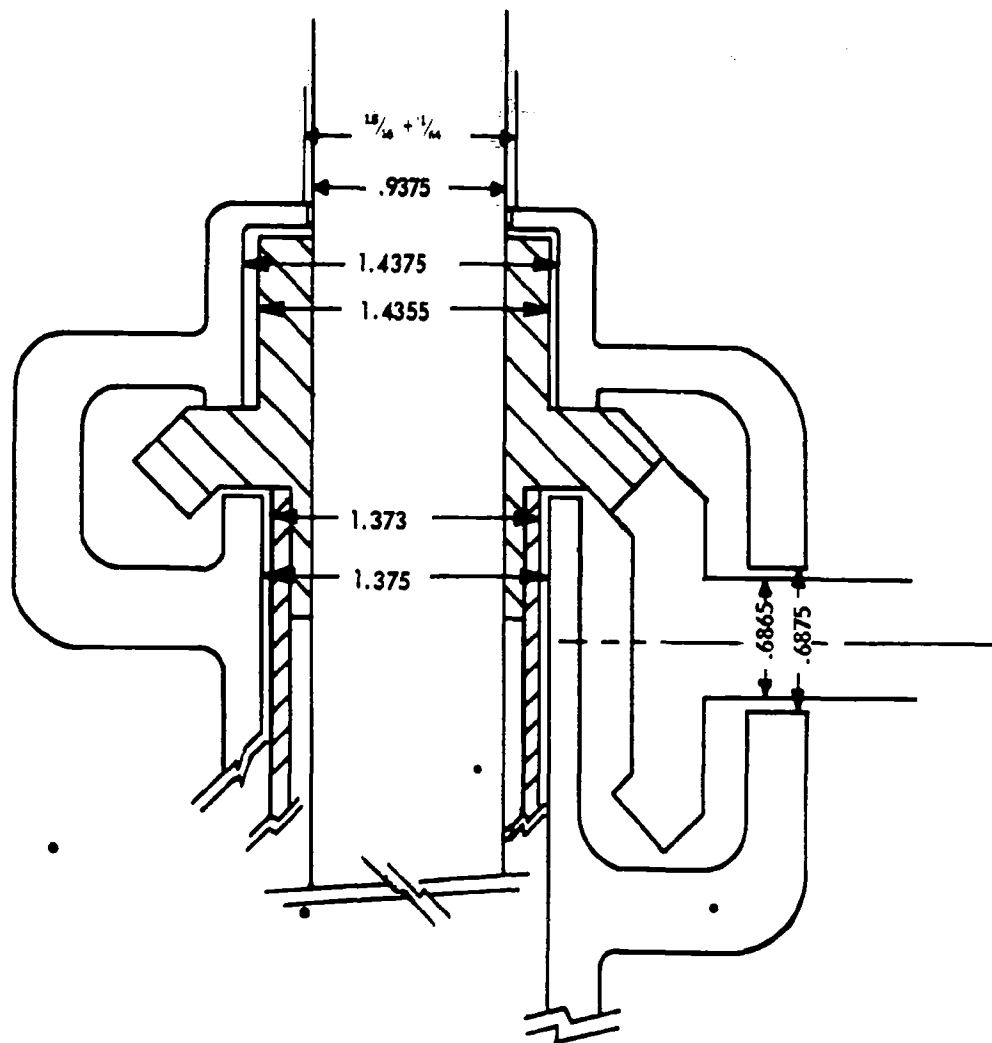


Fig 2 Schematic of elevating mechanism



### Connector

The maximum moment occurs at section AA (see Fig 3), with a moment of inertia equal to

$$I_{AA} = \frac{1}{12}hb^3 = \frac{1}{12} \left(1 \frac{9}{16}\right) \left(1 \frac{5}{16}\right)^3 = .297 \text{ in.}^4$$

and section BB has a smaller moment of inertia

$$I_{BB} = \frac{1}{12} (.312) \left(1 \frac{5}{16}\right)^3 = .174 \text{ in.}^4$$

The corresponding bending moments are

$$M_{AA} = \left(\frac{F''_{avg}}{2}\right) l_1 = \frac{15,140}{2} (1.25) = 9,460 \text{ in.-lb}$$

$$M_{BB} = \frac{15,140}{2} (.72) = 5,440 \text{ in.-lb}$$

and the bending stresses are

$$\sigma_{AA} = \frac{Mc}{I} = \frac{9,460}{.297} \left(\frac{9}{16}\right) = 17,900 \text{ psi}$$

$$\sigma_{BB} = \frac{5,440}{.174} \left(\frac{9}{16}\right) = 17,650 \text{ psi}$$

The shear stress at section CC is,

$$\sigma_{sh} = \frac{F''_{avg}/2}{A} = \frac{\frac{15,140}{2}}{3[2(.312)(.3)]} = 13,500 \text{ psi}$$

The schematic diagram of the elevating mechanism (Fig 2, p 9) indicates the required dimensions of various mating parts. These dimensions were determined in order to preclude binding within the military specifications temperature range of -65°F through 160°F.

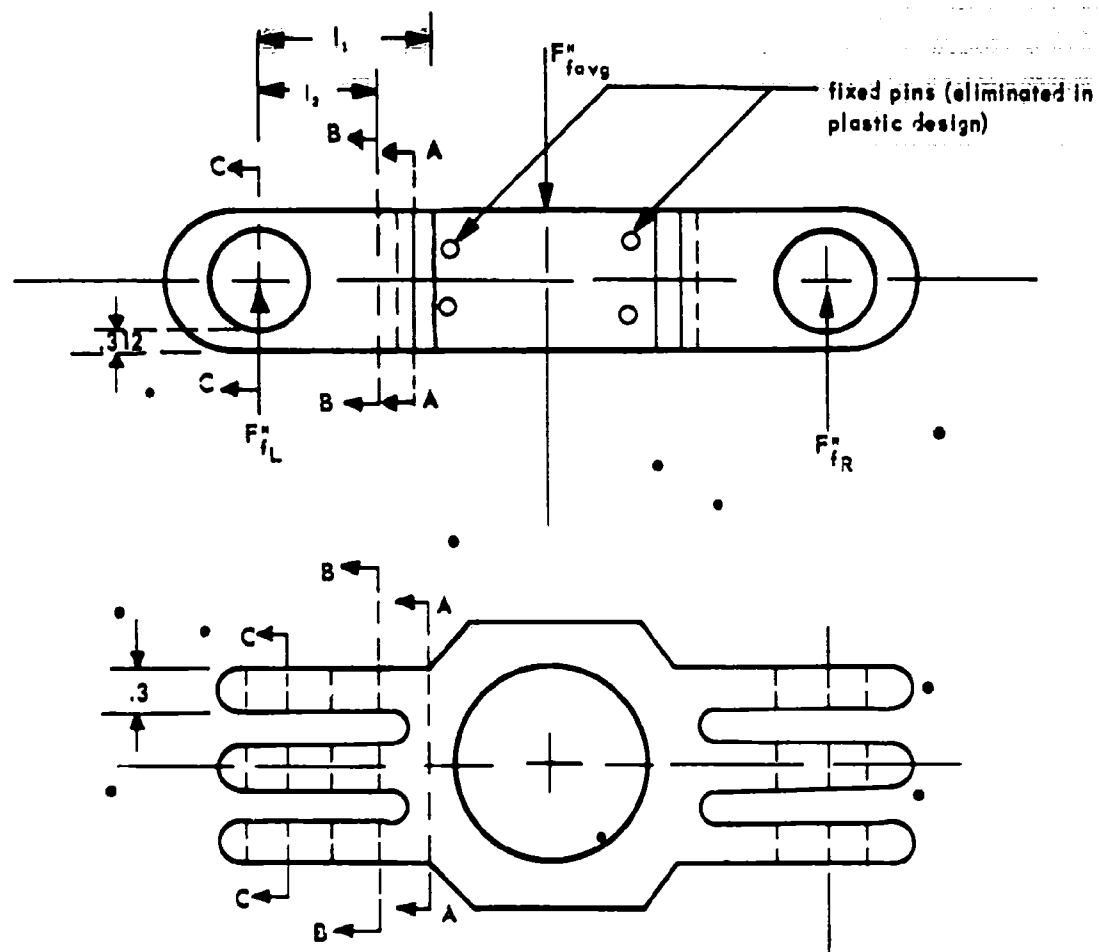


Fig 3 Connector

In terms of stress requirements mentioned above, the bipod assembly components in question can be fabricated from plastics. A molding material such as a fiberglass-filled epoxy should readily fulfill all of the requirements for such plastic parts.

If fabrication of prototype parts is desired this may be accomplished by machining components from rolled tubing. The particular materials suggested for each prototype component are listed below in order of preference (1, 2, 3) on the basis of strength and thermal properties.

Comparison of design stress with the calculated stress values indicates that some of the strength requirements on the rolled tubing materials are marginal. During the analysis, however, the worst possible conditions were used in each case and it is recommended that materials with lower design stress values be test evaluated.

TABLE 1

Composition of component parts

	1		2		3	
	Reinforcement	Resin	Reinforcement	Resin	Reinforcement	Resin
Tube	Cotton cloth	Phenolic	Asbestos	Phenolic	Paper	Phenolic
Case	Cotton cloth	Phenolic	Asbestos	Phenolic	Paper	Phenolic
Bracket	Paper	Phenolic	Asbestos	Phenolic	Cotton cloth	Phenolic
Body	Paper	Phenolic	Asbestos	Phenolic	Cotton cloth	Phenolic
Cover	Paper	Phenolic	Asbestos	Phenolic	Cotton cloth	Phenolic
Connector	Glass	Silicone	Paper	Phenolic	Asbestos	Phenolic
Yoke ring	Glass	Silicone*	Glass	Silicone	Glass	Silicone

\*The silicone glass rolled tubing has the following physical properties:

Thermal coefficient of expansion =  $1.1 \times 10^{-5}$  cm/cm °C

Maximum operating temperature, continuous = 400°F

Maximum operating temperature, short time = 475°F

The reported tensile and compressive strengths for the materials listed in Table I are as follows:

TABLE 2

Material design strength values

Materials Reinforcement	Resin	Material design strength values	
		Tensile strength, psi	Compressive strength, psi
Paper	Phenolic	10,500	17,500
Asbestos	Phenolic	8,500	19,000
Cotton	Phenolic	7,500	21,000
Glass	Silicone	30,000	15,000

The existing parts were redesigned for plastics (see Figs 10-16 in Appendix B, pp 25-31) taking into account the thermal coefficients of expansion of the recommended plastic materials.

Watervliet Arsenal did not request fabrication and testing of the proposed plastic parts. This report, therefore, is a feasibility and design criteria study only.

TABLE 3

Strain data submitted by Watervliet Arsenal

Round Number	Bipod Traverse Position	Angle of Elevation, degrees	Gage Mounted Vertically on					
			Right Bipod Leg			Left Bipod Leg		
			Time,* ms	Strain, $\mu$ in./in.	Stress,** psi	Time,* ms	Strain, $\mu$ in./in.	Stress,** psi
323	Center	45	11.4	-230	-6,670	7.5	-410	-11,890
323	Center	45	40.4	620	17,980	44.6	530	15,370
324	Center	45	12.0	-210	-6,090	8.1	-230	-6,670
324	Center	45	40.2	270	7,830	28.3	320	-9,280
325	Max left	45	8.4	-340	-9,860	8.8	-390	-11,310
325	Max left	45	43.9	380	11,020	44.4	460	13,340
326	Max left	45	8.1	-310	-8,990	-	-	-
326	Max left	45	40.6	600	17,400	-	-	-
327	Max right	45	9.2	-400	-11,600	-	-	-
327	Max right	45	36.4	350	10,150	-	-	-
328	Max right	45	14.2	-440	-12,760	8.3	-390	-11,310
328	Max right	45	38.5	320	9,280	46.5	390	11,310
329	Center	65	16.9	-410	-11,890	11.6	-400	-11,600
329	Center	65	43.9	330	9,570	46.8	520	15,080
330	Center	65	8.4	-370	-10,730	14.1	-260	-7,540
330	Center	65	39.5	370	10,730	33.8	250	7,250
331	Max left	65	15.5	-370	-10,730	7.6	-620	-17,980
331	Max left	65	40.4	320	9,280	44.5	420	12,180
332	Max left	65	8.5	-350	-10,150	9.5	-420	-12,180
332	Max left	65	44.8	360	10,440	46.8	410	11,890
333	Max right	65	8.9	-390	-11,310	9.3	-380	-11,020
333	Max right	65	39.5	250	7,250	45.3	350	10,150
334	Max right	65	7.2	-250	-7,250	10.0	-290	-8,410
334	Max right	65	39.0	240	6,960	44.6	260	7,540
335	Center	73	13.8	-180	-5,220	10.1	-310	-8,990
335	Center	73	56.4	150	4,350	35.0	220	6,380

\*Time from zero time (zero time = time when first deflection is recorded on right leg).

\*\*Stress = strain Y, where Y equals the stretch modulus of elasticity (29 million for gun steel).

The reaction force reported at the base of the mortar barrel was 79,200 pounds.

## APPENDIX A

### Development of Equation for Frictional Force ( $F_f$ )

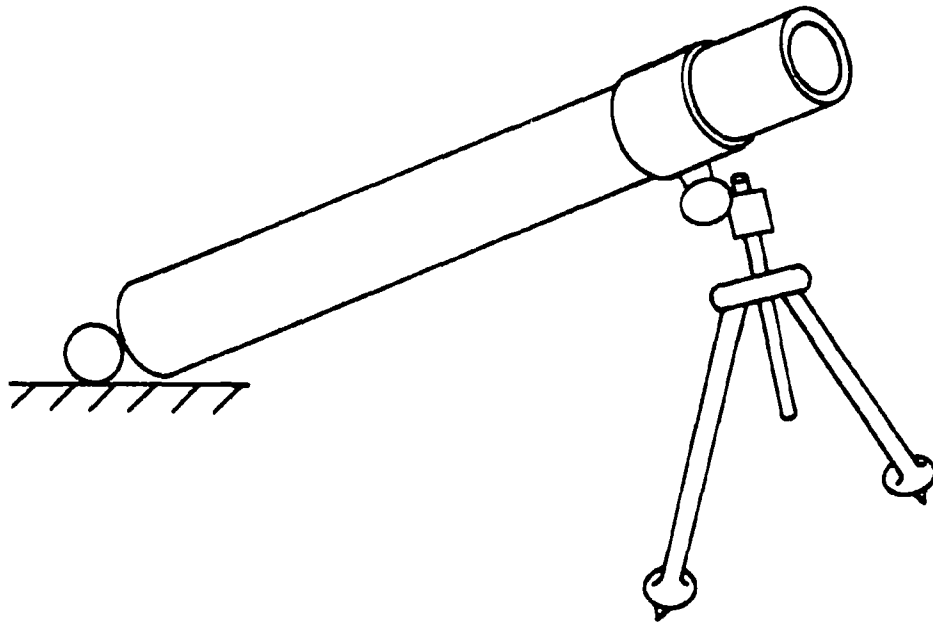


Fig 4 81 mm mortar

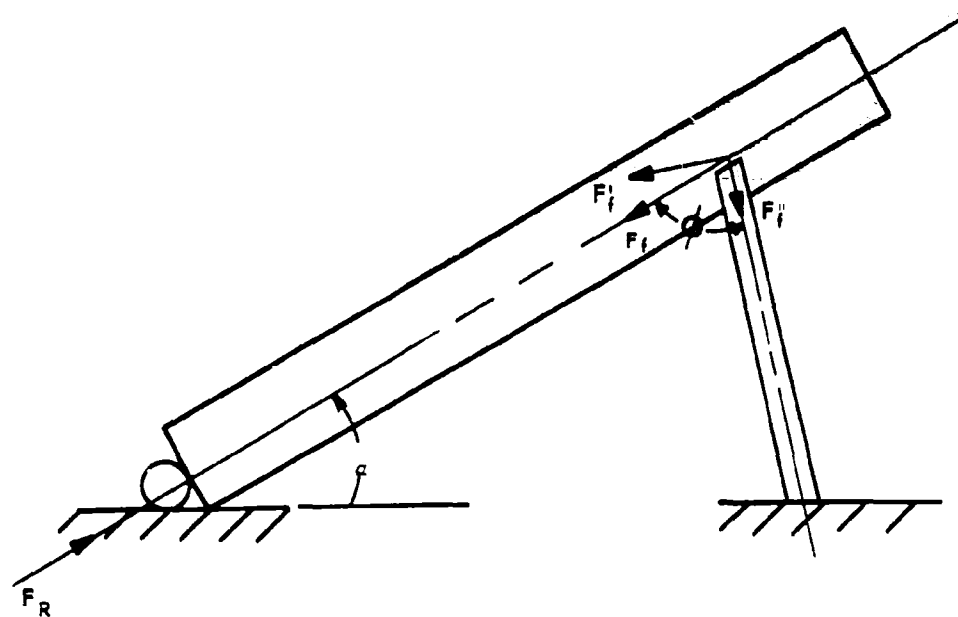


Fig 5 Schematic of force system

$F_R$  = force of recoil

$F_f$  = friction force

$F'_f$  = bending component of friction force

$F''_f$  = compressive component of friction force along center line of bipod assembly, in plane of bipod

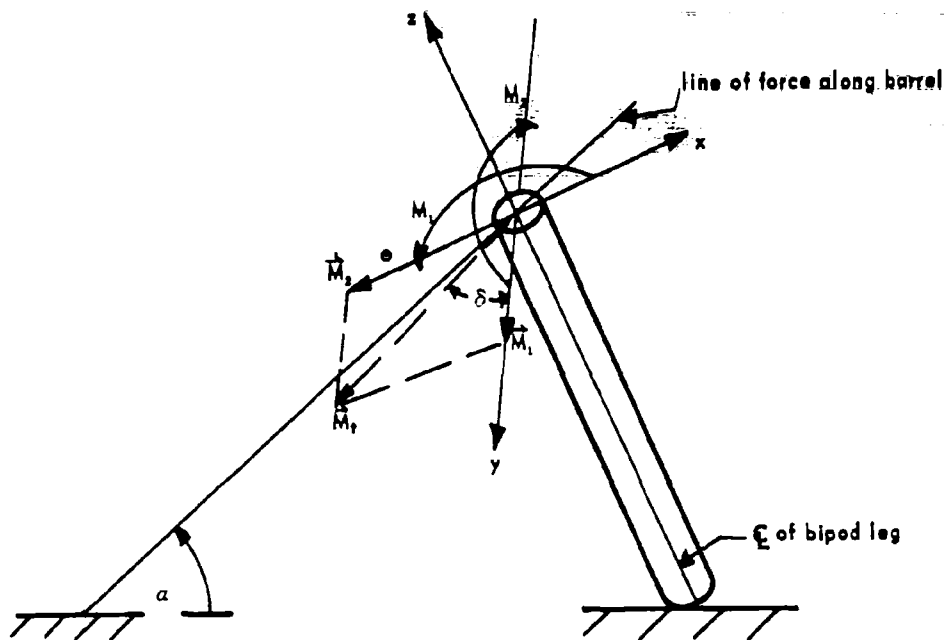


Fig 6 Moment diagram and edge view of bipod assembly

- $M_1$  moment about plane of bipod assembly (x z plane)
- $M_2$  moment in plane of bipod assembly (y z plane)
- $\vec{M}_1$  &  $\vec{M}_2$  moment vectors
- $\vec{M}_t$  resultant moment vector =  $\vec{M}_1 + \vec{M}_2$



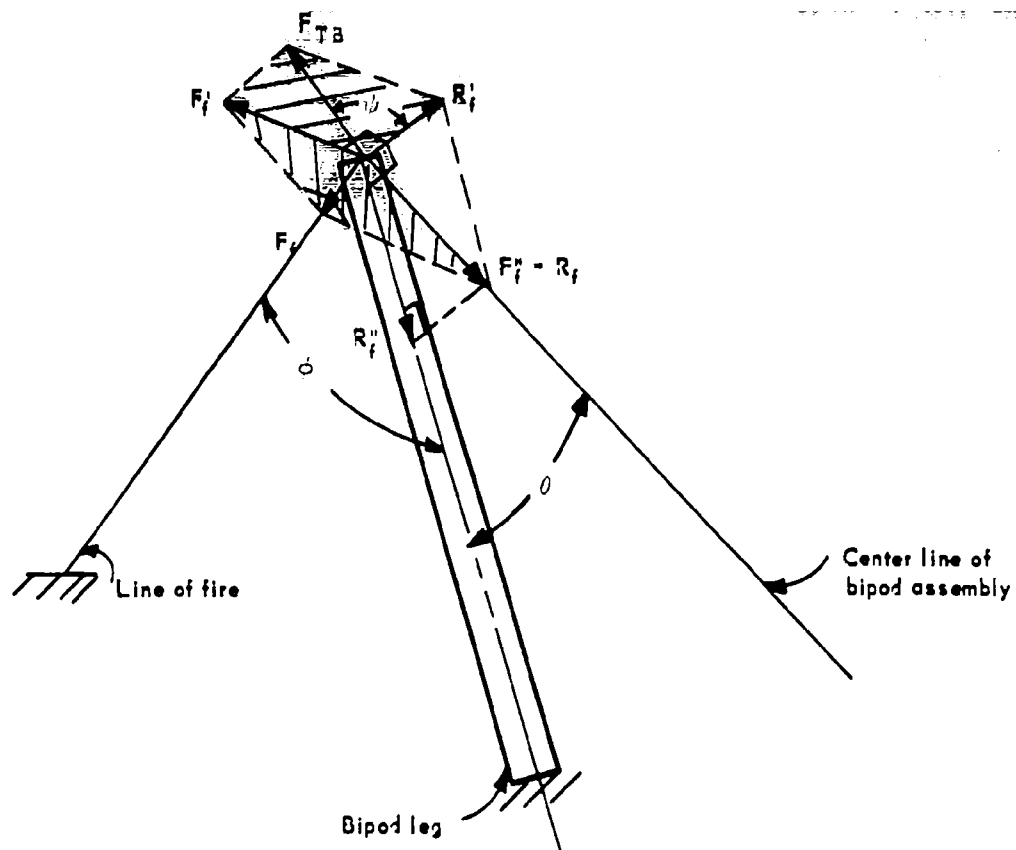


Fig 7 Force diagram


$F_{TB}$  = resultant bending force

$R_f$  = force acting along center line of bipod in the plane of the bipod assembly


$R_f'$  = component of  $R_f$  or  $F_f''$  tending to bend bipod leg

$R_f''$  = component of  $R_f$  compressing bipod leg


Considering one leg of the bipod assembly to act as a cantilever thus bearing half of the applied load, we have

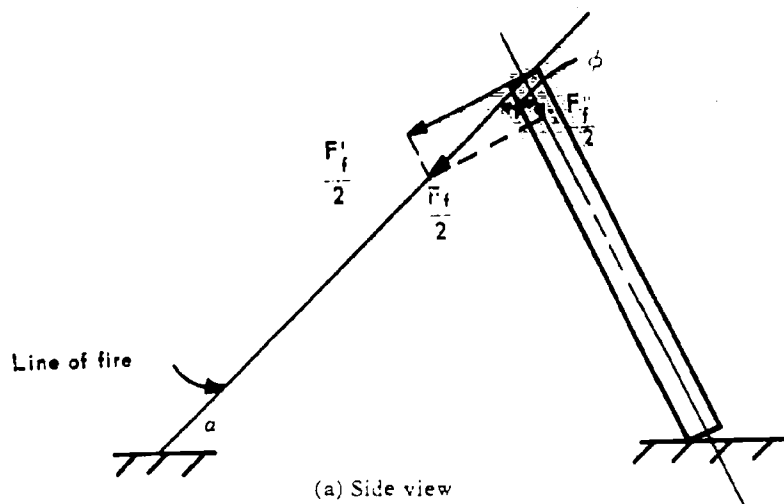

Each leg will bear a load of  $\frac{F_f}{2}$

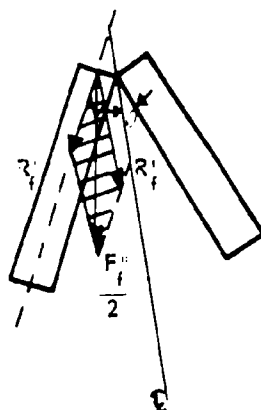

(b) Front view

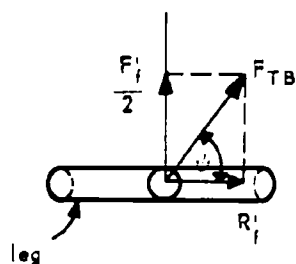

(c) Top view

Fig 8 Bipod assembly

From Figures 8 a, b, and c the following relations are readily determined

$$\left(\frac{F_f}{2}\right)^2 = \left(\frac{F_f^1}{2}\right)^2 + \left(\frac{F_f''}{2}\right)^2 \quad (2a)$$

$$\left(\frac{F_f''}{2}\right)^2 = (R_f^1)^2 + (R_f'')^2 \quad (2b)$$

$$(F_{TB})^2 = \left(\frac{F_f^1}{2}\right)^2 + (R_f^1)^2 \quad (2c)$$

Adding the orthogonal equations (2a), (2b) and (2c) and making the following substitutions:

$$\frac{F_f''}{2} = F_{TB} \sin \psi \quad \left[ R_f^1 = \begin{cases} F_{TB} \cos \psi \\ \frac{F_f''}{2} \sin \theta \end{cases} \right] \quad R_f'' = \frac{F_f''}{2} \cos \theta \quad (2d)$$

we have after simplifying

$$\left(\frac{F_f}{2}\right)^2 = F_{TB}^2 + R_f''^2 \quad (3)$$

The equations for bending and compressive stress for a cantilever are respectively,

$$\sigma_{TB} = \frac{M_T c}{I} = \frac{F_{TB} l c}{I} \quad (\text{Bending}) \quad (4a)$$

solving for  $F_{TB}$

$$F_{TB} = \frac{\sigma_{TB} I}{l c}$$

$$\sigma_c = \frac{R_f''}{A} \quad (\text{compressive}) \quad (4b)$$


solving for  $R_f''$

$$R_f'' = \sigma_c A$$


$l$	length of bipod leg, in.
$c$	distance from neutral axis to extreme fiber, in.
$I$	moment of inertia of bipod leg, in. <sup>4</sup>
$A$	cross sectional area, in. <sup>2</sup>
$F_{TB}$	resultant force causing bending, lb
$R_f''$	compressive force applied to bipod leg, lb
$F_f$	frictional force, lb
$\sigma_{TB}$	tensile stress due to bending, psi
$\sigma_c$	stress due to compression, psi
$\sigma_T$	total stress $\sigma_{TB} + \sigma_c$ , psi.

Substituting equations 4a and 4b into equation 3, we have,

$$F_f = 2 \sqrt{\left( \frac{\sigma_{TB} I}{lc} \right)^2 + (\sigma_c A)^2} \quad (5)$$

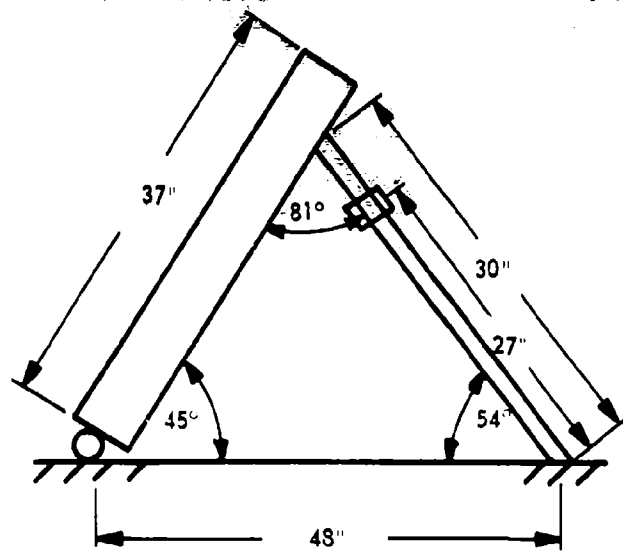

(a) Side view

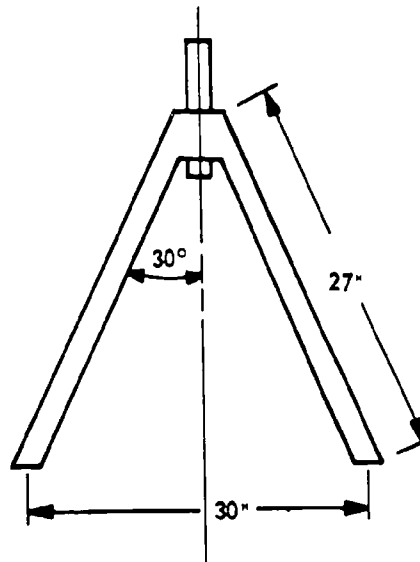

(b) Front view

Fig 9 Assumed geometry of bipod assembly during firing

Using the following values,  $F_f$  is determined as a function of  $\sigma_{TB}$  &  $\sigma_c$

$$I = \frac{\pi}{64} (D_o^4 - D_i^4) = \frac{\pi}{64} [(1.125)^4 - (.875)^4] = .0498 \text{ in.}^4$$

$$l = 27 \text{ in.}$$

$$c = \frac{D_o}{2} = 0.563 \text{ in.}$$

$$A = \frac{\pi}{4} (D_o^2 - D_i^2) = 0.392 \text{ in.}^2$$

Substituting these values into equation (4), the result for the right bipod leg is,

$$F_f = \sqrt{(42.96 \times 10^{-3}) \sigma_{TB}^2 + (.616) \sigma_c^2} \quad (6)$$


Since the geometry and dimensions of the left and right legs differ, Equation 6 is applicable to the right bipod leg only. A similar expression for the left leg is presented in the discussion (Equation 1). Equations 1 and 6 differ only in the coefficients of  $\sigma_{TB}$  and  $\sigma_c$ .

## APPENDIX B

The seven drawings contained in this appendix (Figs 10-16, pp 25-31) show how the components of the 81 mm mortar bipod would have to be changed, in design and dimensions, if they were to be manufactured from plastics. The principal changes shown are:



- a. Relaxation of certain dimensional tolerances from .002 to .003 inch.
- b. Deletion of instructions regarding surface finish.
- c. If grease cups are to be used on bracket, allowance of sufficient clearance for bonding of cups.
- d. A dimensional change of .0055 inch to leave sufficient clearance for bonding between case and housing tube connector.
- e. Elimination of four drill holes in bottom of cylindrical portion of case, because plastic parts would be bonded.
- f. Replacement of a .0615 + .005 inch hole in the case with a  $\frac{1}{16}$  inch ream.
- g. A dimensional change in the yoke ring to permit a clearance of at least .005 inch for bonding of the yoke ring.

- All of the drawings included are modifications of the standard metal parts drawings, to incorporate the above-listed changes.

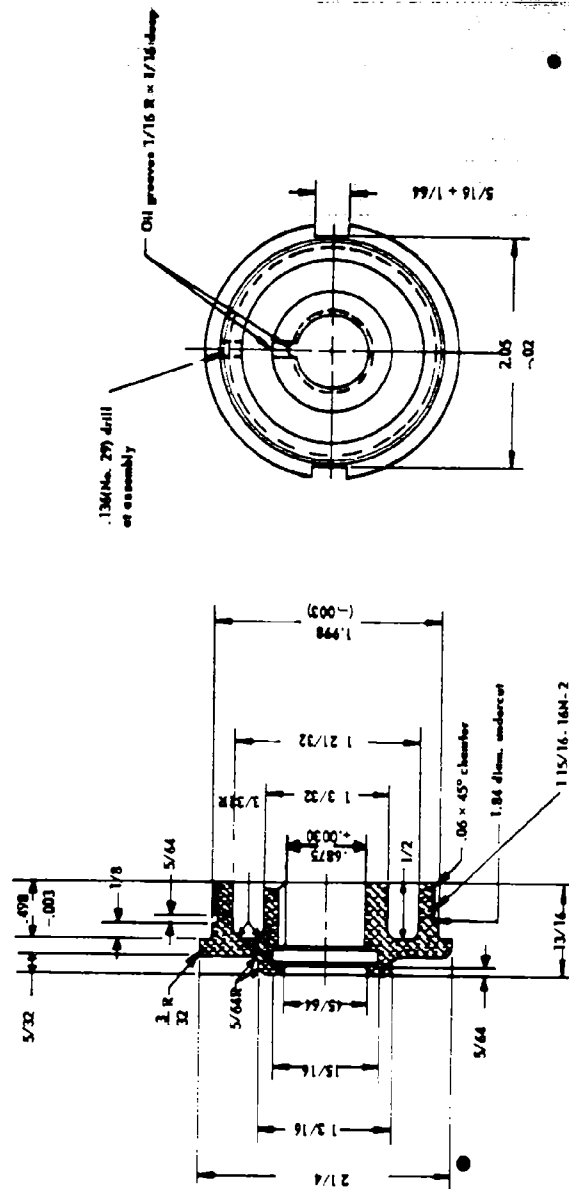

Fillots .01 max





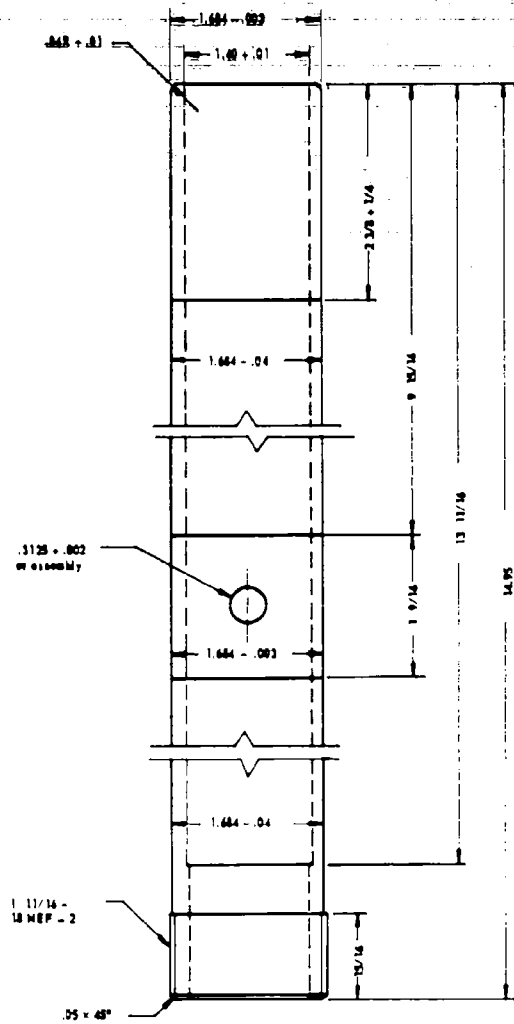

Unless otherwise specified  
break corners approx. .02 max  
fillets .01

Fig 11 Tube (Modification of Dwg 7305150)



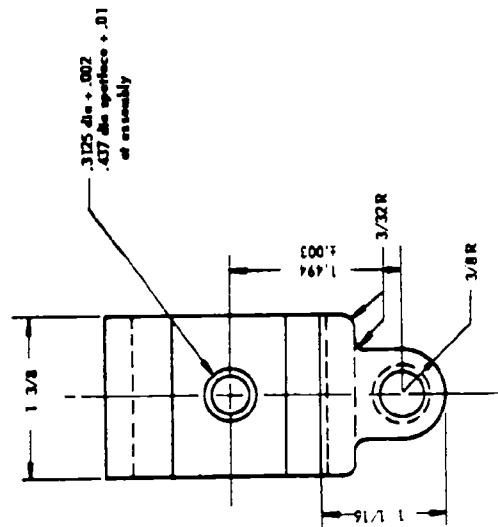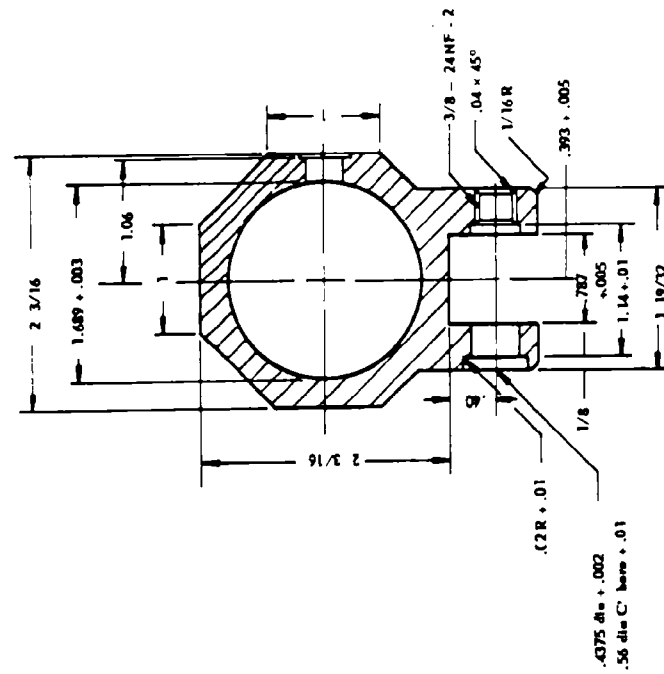

Unless otherwise specified, all  
corners approx. .02 max. R110/15 (3)

Fig 13 Bracket (Modification of Dwg 7305463)




Fig 14 Body (Modification of Dwg 7236576)



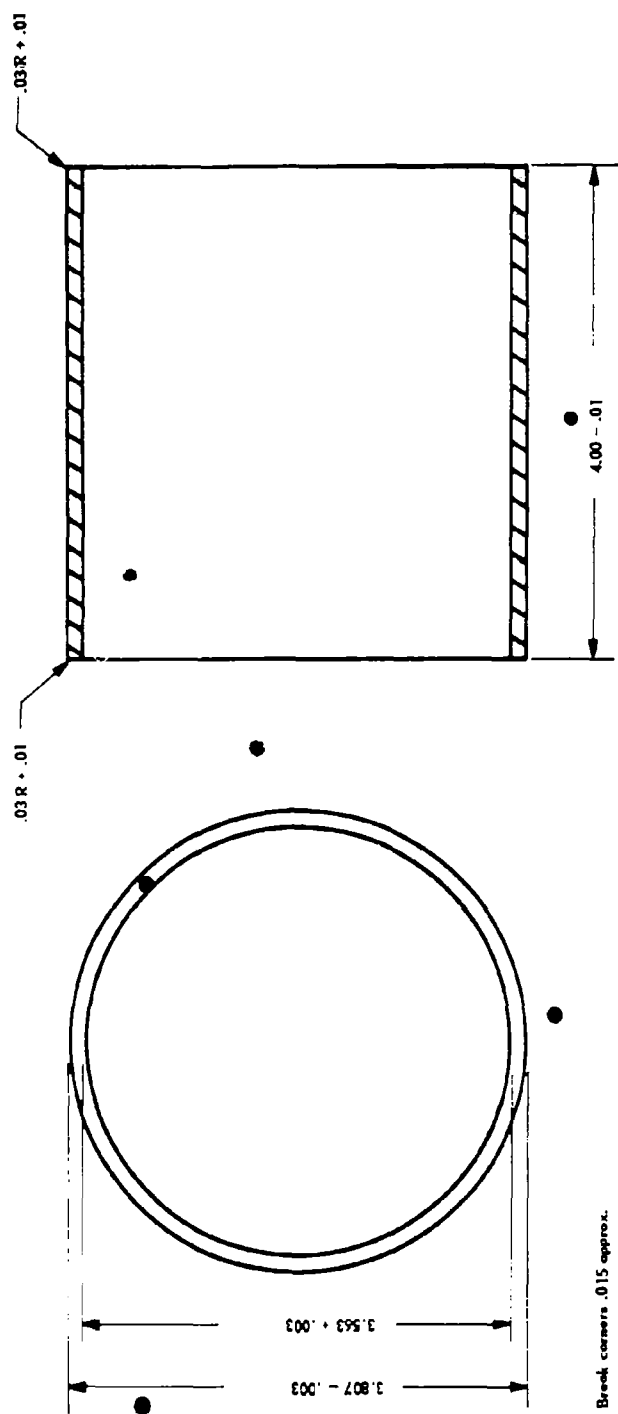


Fig 16 Yoke ring (Modification of Dwg 7305061)

# DISTRIBUTION LIST

Copy No.

Commanding Officer  
Picatinny Arsenal  
ATTN: Technical Information Section  
Dover, N. J.

1 - 5

Commanding Officer  
Army Materiel Command  
Detachment No. 1 (ORD)  
ATTN: Res Div, Dr. Peter Kosting  
Tempo I  
Dept of the Army  
Washington 25, D. C.

6

Commanding General  
Army Munitions Command  
ATTN: AMSMU-A  
          AMSMU-W  
Picatinny Arsenal  
Dover, N. J.

7

8

Plastics Technical Evaluation Center  
ATTN: Director, Mr. H. Peibly  
          A. Molzon  
Picatinny Arsenal  
Dover, N. J.

9 - 10

11

Commanding General  
Ordnance Weapons Command  
ATTN: ORDOW-TX  
Rock Island, Illinois

12 - 13

Commanding General  
Army Ordnance Missile Command  
ATTN: ORDXR-OTL, Technical Library  
          ORDXR-OCF  
Redstone Arsenal, Alabama

14

15 - 19

Commanding Officer	
Detroit Arsenal	
ATTN: ORDMC-RMN, Mr. John Reynar	20
ORDMC-RRS, Mr. D. R. Lem	21
Center Line, Michigan	
Commanding General	
Aberdeen Proving Ground	
ATTN: Coating and Chemical Laboratory	22
Technical Library, ORDBG-LM, Bldg 313	23 - 24
Maryland	
Commanding General	
White Sands Missile Range	
ATTN: ORDES-TS-TIB	25
OM-WSWL, Director WSWL	26
ORDBS, Technical Library	27
New Mexico	
Commanding Officer	
Frankford Arsenal	
ATTN: Pitman-Dunn Labs, Dr. H. Gisser	28
Library Branch, 0270	29
Philadelphia 37, Pa.	
Commanding Officer	
Rock Island Arsenal	
ATTN: Laboratory, Mr. R. F. Shaw	30
Rock Island, Illinois	
Commanding Officer	
U. S. Army Materials Research Agency	
ATTN: RPD	31
Watertown Arsenal	
Watertown 72, Mass.	
Commanding Officer	
Springfield Armory	
ATTN: Res Chem Lab, Mr. Zavarella	32
Springfield 1, Mass.	



Commanding Officer Watervliet Arsenal ATTN: ORDBF-RR Watervliet, N. Y.	33
Commanding General U. S. Army Ordnance Guided Missile School Redstone Arsenal, Alabama	34
Commanding Officer Ammunition Procurement & Supply Agency ATTN: SMUAP Joliet, Illinois	35
Commanding General Ordnance Tank-Automotive Command ATTN: ORDMG-11-60 Detroit Arsenal Center Line, Michigan	36
Commanding Officer Watertown Arsenal ATTN: Technical Information Section Watertown 72, Mass.	37
Commanding Officer Harry Diamond Ordnance Fuze Laboratories ATTN: Technical Reference Section A. A. Benderly Connecticut Ave and Van Ness St, NW Washington 25, D. C.	38 39
Commanding General U. S. Army Signal Research and Development Laboratories ATTN: SIG-FM/EL-PEM-1-d Mr. E. Beekman Fort Monmouth, N. J.	40 41

Chemical Corps Chemical Research and Development Labs ATTN: Mr. T. A. Treglia Army Chemical Center, Maryland	42
Chemical Corps Chemical Center and Chemical Corps Materiel Command ATTN: Mr. A. A. Cooke, CMLAM-M-2P-44 Army Chemical Center, Maryland	43
Commanding Officer Engineer Research and Development Laboratories Materials Branch ATTN: Mr. Philip Mitton Mr. S. Goldfein Fort Belvoir, Virginia	44 45
Commanding General Quartermaster Research and Engineering Center ATTN: Clothing and Organic Materials Div Natick, Mass.	46 - 48
Office, Chief of Transportation Dept of the Army ATTN: Mr. John Stolarick, TCARO-R Washington 25, D. C.	49
U. S. Army Transportation Research Command Fort Eustis ATTN: Mr. J. E. Forehand, Aviation Directorate Mr. H. I. Krellen, Surface Mobility Directorate Virginia	50 51
Dept of the Navy Office of Naval Research ATTN: Code 423 Washington 25, D. C.	52

Dept of the Navy  
Bureau of Ships  
Hull Division  
Materials Development and Applications Branch  
ATTN: Mr. J. B. Alfors, Code 634C  
Washington 25, D. C.

53

U. S. Naval Ordnance Laboratory  
ATTN: Mr. H. A. Perry  
Mr. F. R. Barnet, Chief, Nonmetallic  
Materials Division

54

55

White Oak  
Silver Spring, Maryland

Commander  
Naval Research Laboratory  
ATTN: Technical Information Officer  
Anacostia Station  
Washington 25, D. C.

56

Commander  
New York Naval Shipyard  
ATTN: R. R. Winans  
Material Laboratory (Code 948)  
Brooklyn 1, N. Y.

57

Dept of the Navy  
Bureau of Naval Weapons  
ATTN: RRMA  
Airborne Equipment Division  
Washington 25, D. C.

58

59

Dept of the Navy  
Bureau of Supplies and Accounts  
ATTN: Mr. H. Lapidus  
Code S-82  
Washington 25, D. C.

60

Naval Weapons Station  
Research and Development Division  
ATTN: Mr. U. Cormier  
Yorktown, Virginia

61

Aeronautical Materials Laboratory  
Naval Air Materials Center  
ATTN: Mr. E. K. Rishel, Head, Plastics Branch  
Philadelphia 12, Pa.

62

Naval Weapons Laboratory  
ATTN: Mr. R. Tom (Code WCD)  
Dahlgren, Virginia

63

Dept of the Navy  
Bureau of Naval Weapons Research,  
Development Test, and Development  
ATTN: Mr. P. M. Goodwin, Head, Nonmetals  
Branch (RRMA-3)  
Washington 25, D. C.

64

Naval Air Development Center  
Aeronautical, Electronic, and Electrical Laboratory  
ATTN: Dr. H. R. Moore, Head, Materials and  
Process Branch  
Johnsville, Pa.

65

Commander (Code 5557)  
U. S. Naval Ordnance Test Station  
Inyokern  
China Lake, California

66

David Taylor Model Basin  
ATTN: Mr. A. R. Willner, Head, Materials  
Research Branch  
Washington 7, D. C.

67

• Commander Aeronautical Systems Division Wright-Patterson Air Force Base ATTN: Mr. R. T. Schwartz, ASRCNC Mr. Peterson, ASRCNC-1 Dayton, Ohio	68 69
Armed Services Technical Information Agency Arlington Hall Station Arlington 12, Virginia	70 - 79
Dr. W. R. Lucas (M-S and M-M) George C. Marshall Space Flight Center Huntsville, Alabama	80
Sandia Corporation Sandia Base Albuquerque, N. M.	81
Sandia Corporation Livermore Laboratory ATTN: Librarian P. O. Box 969 Livermore, California	82
Interservice Data Exchange Program AOMC IDEP Office ATTN: R. A. Ham, ORDXM-RCS Redstone Arsenal, Alabama	83 - 84
Commanding Officer Watervleit Arsenal ATTN: ORDBB-VP Watervleit, N. Y.	85 - 89
Commander Naval Research Laboratory ATTN: Joseph Kies (Code 6210) Anacostia Station Washington 25, D. C.	90

Copy No.

David Taylor Model Basin  
Structural Mechanics Laboratory  
ATTN: Mr. J. Buhl (Code 732)  
Washington 7, D. C.

91

Commanding General  
Manufacturing Technique Laboratory  
Aeronautical System Division  
Chemical Engineering Branch  
Wright-Patterson Air Force Base  
ATTN: Mr. Charles Tanis  
Dayton, Ohio

92

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963, 39 pp, tables, figures. DA Proj 593-32-007, OMS 5010. 11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

1. Mortars, 81 mm — Materials
2. Epoxides — Applications
3. Glass reinforced plastics — Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Eig, M.

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963, 39 pp, tables, figures. DA Proj 593-32-007, OMS 5010. 11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963, 39 pp, tables, figures. DA Proj 593-32-007, OMS 5010. 11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

1. Mortars, 81 mm — Materials
2. Epoxides — Applications
3. Glass reinforced plastics — Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Eig, M.

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963, 39 pp, tables, figures. DA Proj 593-32-007, OMS 5010. 11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

1. Mortars, 81 mm — Materials
2. Epoxides — Applications
3. Glass reinforced plastics — Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Eig, M.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Rolled reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Rolled reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Rolled reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Rolled reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.



AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963,  
39 pp, tables, figures. DA Proj 593-32-007, OMS 5010.  
11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

1. Mortars, 81 mm —  
Materials
2. Epoxides — Applications
3. Glass reinforced  
plastics — Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Eig, M.

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963,  
39 pp, tables, figures. DA Proj 593-32-007, OMS 5010.  
11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963,  
39 pp, tables, figures. DA Proj 593-32-007, OMS 5010.  
11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963,  
39 pp, tables, figures. DA Proj 593-32-007, OMS 5010.  
11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

1. Mortars, 81 mm —  
Materials
2. Epoxides — Applications
3. Glass reinforced  
plastics — Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Eig, M.

1. Mortars, 81 mm —  
Materials
2. Epoxides — Applications
3. Glass reinforced  
plastics — Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Eig, M.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Roller reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Roller reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Roller reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Roller reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963, 39 pp, tables, figures. DA Proj 593-32-007, OMS 5010. 11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

1. Mortars, 81 mm --  
Materials
2. Epoxides -- Applications
3. Glass reinforced plastics -- Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Fig. M.

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963, 39 pp, tables, figures. DA Proj 593-32-007, OMS 5010. 11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963, 39 pp, tables, figures. DA Proj 593-32-007, OMS 5010. 11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

1. Mortars, 81 mm --  
Materials
2. Epoxides -- Applications
3. Glass reinforced plastics -- Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Fig. M.

AD \_\_\_\_\_ Accession No. \_\_\_\_\_  
Feltman Research Laboratories  
Picatinny Arsenal, Dover, N. J.

**FEASIBILITY STUDY ON THE USE OF PLASTIC COMPONENTS FOR THE 81 MM MORTAR BIPOD ASSEMBLY**

Merrill Eig

Picatinny Arsenal Technical Report 3030, February 1963, 39 pp, tables, figures. DA Proj 593-32-007, OMS 5010. 11.842. Unclassified Report

Strain data obtained during firing from gages positioned on the legs of the 81 mm mortar bipod assembly was reported to Picatinny Arsenal by Watervliet Arsenal. The forces exerted on the bipod assembly were determined by analyzing this data. Once this was accomplished the individual forces acting upon components could be calculated. A 45° elevation was used, with the bipod traverse assembly located in the central position.

(over)

1. Mortars, 81 mm --  
Materials
2. Epoxides -- Applications
3. Glass reinforced plastics -- Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Fig. M.

1. Mortars, 81 mm --  
Materials
2. Epoxides -- Applications
3. Glass reinforced plastics -- Applications
1. Eig, Merrill

**UNITERMS**

Plastics  
Glass fabrics  
Epoxides  
81 mm  
Mortar  
Base  
Assembly  
Bipod  
Fig. M.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing.<sup>4</sup> The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Roller reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Roller reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Roller reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.

The calculated maximum stresses were as follows: a bearing stress of 20, 100 psi on the case; and a 2780 psi stress due to bending, and a compressive stress of 22,880 psi for the tube housing. The cover, body, and yoke ring were not significantly stressed. The connector showed a bending stress of 17,900 psi and a shear stress of 13,500 psi.

Roller reinforced plastic tubing was suggested for fabrication of prototype components, as it can be easily machined to the desired shapes and has the required strength. It should be noted that the design strength of the tubing is marginal.

For end items, a glass-filled epoxy compression molding compound such as Scotchply 1100 would have the desired strength and other required physical properties.

The components were redesigned for fabrication from plastics. The recommended design changes are shown in an Appendix.